

**2-D Nano Materials and their  
Hybrids as Supercapacitor  
Electrodes for Energy Storage  
Applications**

**Thesis submitted for the partial fulfilment of the  
requirements for the degree of  
Doctor of Philosophy in Science**

**by**

**Shibsankar Dutta**

**Under Supervision of  
Dr. Sukanta De**

**Department of Physics  
Faculty of Natural and Mathematical Sciences Departments  
Presidency University  
Kolkata-700073, India**

**2019**

**Thesis Title: *2-D Nano Materials and their Hybrids as Supercapacitor Electrodes for Energy Storage Applications***

**Name of the Candidate: *Shibsankar Dutta***

**Registration Number: *R-14RS09110068***

**Date of Registration: *12/08/2016***

**Department: *Physics***

*Shibsankar Dutta*  
02/09/19  
**Signature of the Candidate with date**

## Conclusions and Future works

The main focus of this dissertation is to get a better understanding about the electrochemical behaviour of the 2-D nano materials to fabricate of hybrid SCs with the carbonaceous electrode materials using aqueous and solid (gel electrolyte) electrolytes for two electrode and three electrode supercapacitor applications.

Present work reported large scale production of 2-D materials using mixed solvent exfoliation from their bulk forms and Hydro (or solvo) thermally synthesized layered materials also exfoliated by liquid phase exfoliation by suitable solvents. These well dispersed stable solutions were used to make thin films which can be readily transferred on wide range of substrates for flexible supercapacitor electrode applications with high energy density. The performance of the composite electrode materials by varying compositions also included in the present work. The specific novelty claims in this thesis are listed below

- Mixed solvent exfoliation of 2-D nano materials.
- Few layered 2-D materials and their hybrids or composites with graphene and CNTs thin films on different substrates for flexible supercapacitor application
- An investigation the performance of 2-D materials based solid state supercapacitor varying compositions and optimised the best composition endowed with high energy density.

The following points emerged as conclusions from the detail works done described in the thesis:


1. A systematic study was done to prepare the 2-D nanosheets of TMOs from their bulks by mixed solvent exfoliation using ethanol and water. The results concludes two poor solvents ethanol and water can be a good solvent for exfoliating TMOs when they combined in a particular volume fraction. The versatile mixed solvent method is scalable and gives high concentration (0.42 mg/ml, 0.47 mg/ml and 0.40 mg/ml for MoO<sub>3</sub>, MnO<sub>2</sub> and RuO<sub>2</sub> respectively) dispersion of TMOs nanosheets, higher than that reported previously. We have quantitatively analyzed the absorption spectra for all dispersions to optimize the volume fractions of water and ethanol to disperse TMOs. The results showed concentrations of TMOs dispersions are directly dependent on the volume fraction of ethanol in water with maximum concentration at 65% ethanol in water for MoO<sub>3</sub>. Whereas for both MnO<sub>2</sub> and RuO<sub>2</sub> maximum concentration was obtained at 50%

mixed solvent. This mixed-solvent strategy gives great freedom to the researchers to design ideal solvent system from unlimited number of possible solvent mixture for various layered materials to exfoliate. Exfoliation of TMOs in mixture of two low boiling point solvents offers obvious advantages, including low cost, less toxicity compare to previously used organic solvents, no additive required, and easy removal. AFM and HRTEM and FESEM study shows that mostly bi-layer nanosheets are with average lateral size of 300 nm for MoO<sub>3</sub>, 200 nm for MnO<sub>2</sub> and 100 nm for RuO<sub>2</sub> were obtained. The exfoliated nanosheets obtained specific surface area of 55.7 m<sup>2</sup> /g, 48.6 m<sup>2</sup> /g, 53.5 m<sup>2</sup>/ g for MoO<sub>3</sub>, MnO<sub>2</sub> and RuO<sub>2</sub> nanosheets respectively. Whereas, the total specific surface area of 151.4 m<sup>2</sup> /g, 122.8 m<sup>2</sup> /g, 142.6 m<sup>2</sup> /g were obtained for the MoO<sub>3</sub>/SWCNT, MnO<sub>2</sub>/SWCNT and RuO<sub>2</sub>/SWCNT nanocomposites respectively. The large specific surface area and mesoporous structure provides more active sites and shortening ion diffusion paths between electrode and electrolyte for electrochemical reactions, which reflected in the electrochemical result obtained for SWCNT/TMOs thin films supercapacitor. The MoO<sub>3</sub>/SWCNT flexible symmetric solid state supercapacitor delivered maximum specific capacitance of 717 F/g at 5 mV/s, whereas MnO<sub>2</sub>-SWCNT and RuO<sub>2</sub>-SWCNT symmetric supercapacitor exhibited a specific capacitance of 540 F/g and 676 F/g respectively. The symmetric supercapacitors exhibit excellent flexibility and long cycle life, leading to an extremely high energy density (24.89 Wh/Kg at 1.61 kW/kg, 18.73 Wh/Kg at 1.21 kW/Kg and 23.48 Wh/Kg at 1.52 kW/Kg), whereas, in-plane micro supercapacitors based on few layered MnO<sub>2</sub> and SWCNT hybrid displayed excellent specific capacitance of 560.22 F/g with significant energy density of 77.80 Wh/kg.

2. A systematic study was conducted for the synthesis of BiVO<sub>4</sub> nanoparticle by varying the hydrothermal reaction conditions. The well crystalline BiVO<sub>4</sub> nanoparticles having almost same in shape and size with an average dimension of ~20–30 nm are obtained at the optimum growth duration of 90 min. The growth mechanism of the morphology was investigated by SEM analysis. We have also synthesized BiVO<sub>4</sub> embedded rGO hybrid nanostructure with three different GO concentrations by a simple cost effective hydrothermal method. Structure, surface morphology and capacitive behaviours of BiVO<sub>4</sub>/rGO hybrid were well investigated. We have studied the electrochemical

properties of as prepared hybrid to know its performance as symmetric supercapacitor electrodes with both PVA/H<sub>2</sub>SO<sub>4</sub> solid and Na<sub>2</sub>SO<sub>4</sub> aqueous electrolytes. The obtained maximum specific capacitance is 400 F/g at 5 mV/s scan rate in solid electrolyte and 245 F/g in aqueous Na<sub>2</sub>SO<sub>4</sub> at same scan rate. High energy density (35.37 Wh/Kg) and excellent cycle stability makes this hybrid suitable for application in supercapacitor.

3. Well crystalline BiOCl nanoplates were prepared by simple hydrothermal route. BiOCl /MWCNT based nanocomposites with different weight percentage of BiOCl as electrodes were designed for light-weight flexible high performance thin film supercapacitor. As prepared nanoplates was characterized by XRD, Raman, FESEM, TEM and XPS. The N<sub>2</sub> adsorption–desorption measurement result shows among different compositions, composite with 60 wt% BiOCl exhibits maximum specific surface area of 22.750m<sup>2</sup>/g . The 60 wt% BiOCl composite flexible supercapacitor delivered highest specific capacitance of 421F/g and energy density 14.62 Wh/Kg. Excellent cycle stability with only 6% reduction in specific capacitance after 2000 cycles and good stability under bending, making the fabricated supercapacitor extremely promising as a flexible energy storage device.
4. MoS<sub>2</sub> nano sheets and MoS<sub>2</sub>/rGO hybrid also synthesized by hydrothermal route. The thin film of hybrid electrodes on an Au coated PET obtained specific capacitance of 14.09mF/cm<sup>2</sup> at 5mV/s, much higher than that of only MoS<sub>2</sub> electrodes 0.79mF/cm<sup>2</sup> at the same scan rate. Hybrid electrode exhibits high energy density of 5.71mWh/cm<sup>2</sup> and a power density of 54.1mW/cm<sup>2</sup>. The composite electrode exhibits an excellent stability after 1000 cycles.
5. Vanadyl phosphate nano sheets/MWCNT free standing thin films were prepared by si by vacuum filtering. The nanocomposite electrode yielded a specific capacitance of 236 F/g at the scan rate 5 mV/s much higher than that of MWCNT electrodes (49 F/g) at the same scan rate. The nanocomposite electrode exhibited energy density of 65.6 Wh/Kg at a power density 1476 W/Kg. could be a good candidate for electrode of supercapacitor with superior energy efficiency. Fig.1 represents the Ragone plot of our 2-D material based supercapacitor compare with reported literature. Overall, the work based on the 2-D nanomaterials presented in this thesis mostly enhanced the energy storage performance of the supercapacitors towards light weight flexible energy storage device applications.

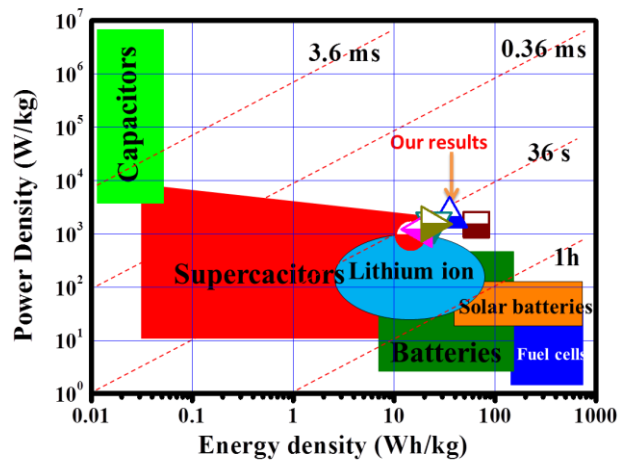

**Figure 1.** Ragone plot of our 2-D material based supercapacitor compare with reported literature.

### Future Works

In recent years due to the fast development of electronic devices including flexible smart window, flexible transparent touch screens, electronic books etc., investigation on flexible transparent electrodes has attracted huge attention.<sup>1-5</sup> commercially available transparent ITO (Indium tin oxide) electrode may be replaced by carbon nanotubes (CNTs)<sup>6</sup>, graphene<sup>7</sup>, metal nanowires<sup>8</sup>, Conductive polymers based transparent electrode to improve the performance of supercapacitor. Energy density is directly proportional to the square of the voltage window as well as the capacitance value, so enhancement of the energy density can be done by increasing both voltage window and capacitance value. Adding redox-active materials such as copper chloride, potassium iodide, hydroquinone etc. into the electrolytes is an easy process to improve the electrochemical performances because of extra pseudo capacitance contribution from the redox active electrolyte at the electrode-electrolyte interface.

Some of the future prospects of these present research works can be explored as follows

1. BiOCl/SWCNT based flexible transparent high performance supercapacitors.
2. Fe<sub>2</sub>O<sub>3</sub>/SWCNT based flexible transparent thin film supercapacitor with AgNWs as current collector.

3. Improve electrochemical performance of BiOCl/rGO supercapacitors after adding redox-active materials to the electrolyte.

### 9.3 References

1. S. De, P.E. Lyons, S. Sorel, E.M. Doherty, P.J. King, W.J. Blau, P.N. Nirmalraj, J.J. Boland, V. Scardaci, J. Joimel, J.N. Coleman, *ACS Nano*, 2009, **3**, 714–720.
2. H.Z. Geng, K.K. Kim, K.P. So, Y.S. Lee, Y. Chang, Y.H. Lee, *J. Am. Chem. Soc.*, 2007, **129**, 7758–7759.
3. Y. Zhou, F. Zhang, K. Tvingstedt, S. Barrau, F. Li, W. Tian, O. Inganäs, *Appl. Phys. Lett.*, 2008, **92**, 2006–2009.
4. G. Eda, Y.Y. Lin, S. Miller, C.W. Chen, W.F. Su, M. Chhowalla, *Appl. Phys. Lett.*, 2008, **92**, 10–13.
5. W. Hong, Y. Xu, G. Lu, C. Li, G. Shi, *Electrochem. Commun.*, 2008, 101555–1558.
6. X. Wang, L. Zhi, K. Müllen, *Nano Lett.*, 2008, **8**, 323–327.
7. S. Bae, H. Kim, Y. Lee, X. Xu, J.S. Park, Y. Zheng, J. Balakrishnan, T. Lei, H. Ri Kim, Y. Il Song, Y.J. Kim, K.S. Kim, B. Özyilmaz, J.H. Ahn, B.H. Hong, S. Iijima, *Nat. Nanotechnol.*, 2010, **5**, 574–578.
8. J. Lee, P. Lee, H.B. Lee, S. Hong, I. Lee, J. Yeo, S.S. Lee, T.S. Kim, D. Lee, S.H. Ko, *Adv. Funct. Mater.*, 2013, **23**, 4171–4176
9. N. Kim, S. Kee, S.H. Lee, B.H. Lee, Y.H. Kahng, Y.R. Jo, B.J. Kim, K. Lee, *Adv. Mater.*, 2014, **26**, 2268–2272.